

Analysis of Micro Vickers Hardness of Friction Stir Welding of Dissimilar Aluminum Alloys (AA6061-T6 and AA6082-T6)

Gurvir Singh Suri^{1*}, Gurmeet Kaur² and Balwant Singh Luthra¹

¹ME Department, Chandigarh University, Mohali, 141013, Punjab, India; gurvirsuri@gmail.com, cubalwant@gmail.com

²ME Department, GNDEC, Ludhiana - 141006, Punjab, India; gill_gurmeetkaur@yahoo.co.in

Abstract

Objectives: Friction Stir Welding method is used to join two metals or alloys with the help of rotating tool along the butt edges of the workpieces. The material reaches recrystallization temperature which leads to formation of high strength weld without the melting of joining materials. In this research, the dissimilar aluminum alloy plates (AA6061 and AA6082) of 6 mm thickness were Friction Stir Welded and mechanical properties were investigated. **Methods/Analysis:** Experiment was performed using Taguchi L9 technique and the different plates were welded with the help of friction at different tool rotational speeds of 800, 1100 and 1400 rpm by shifting the welding speeds i.e. 180, 150 and 120 mm/min and tool profiles (cylindrical threaded and taper threaded). **Findings:** It was concluded from the present study that the average value of hardness was lower compared to base alloy at the zone of nugget. **Novelty/Improvement:** Friction Stir Welding procedure can be economically utilized as a part of welding of different aluminum compounds.

Keywords: Friction Stir Welding

1. Introduction

Friction Stir Welding (FSW) is a framework in welding in which an characteristic tool is used to create frictional warmth at the welding region where metal material will be changed over into solid state¹. Friction Stir Welding is a moderately new strong state joining process². This joining procedure is energy efficient, environment well disposed, and adaptable³. Specifically, it can be utilized to join high-quality aviation aluminum alloys and different composites of metal that are difficult to be welded by traditional combination welding⁴. FSW is thought that it is best method of welding and most significant for the improvement in metal joining. This procedure is principally utilized on aluminum and regularly on substantial pieces, which can't be effortlessly warm treated, post weld to recoup temperature attributes⁵. The Friction Stir Welding is really, another innovation in the high execution aviation and car application. In contrast

with conventional welding systems, FSW unequivocally lessens the nearness of contractions⁶.

Aluminium alloys are basically used in industry due to its better corrosion resistance, high electrical and thermal conductivity⁷. The welding of the two different Cu alloys cannot be done easily with the help of conventional welding process due to which welding was done by friction stir method. The different alloys such as aluminium, magnesium, copper, ferrous and titanium were welded with the help of friction stir from last few years⁸. The welding process which is done by conventional process suffers from various types of defects such as porosity and in these pores gases entrapped which was not escaped during solidification⁹. The welding in which friction stir was used having non consumed rotating tool also maintained temperatures below melting point of materials being joined. It is difficult in joining materials with vastly different composition of materials with the help of conventional process of fusion welding¹⁰. The

* Author for correspondence

selection of appropriate filler material having intermediate properties is critical¹⁰.

2. Experimentation

The material utilized for the trial work was AA6061 and AA6082 plates with measurements (100 mm x 50 mm x 6 mm). The VMC machine was utilized for welding purposes. The installation Figure 1 was utilized for completing test work. The high speed steel tools¹¹ were utilized for completing the Friction Stir Welding process. In the present study three distinctive instrument pin profiles were taken to examine hardness of welded sample. The distinctive pin profiles utilized as a part of this study are displayed in Figure 2.

The process parameters are rotational speed of tool, feed rate of tool and pin profile of tool¹². The Taguchi L9 orthogonal array method was used for the different optimization with different inputs. The working parameters as shown in Table 1 implemented in this study are taken after different trials. The three levels are taken for each process parameter. Vickers micro hardness tests were completed on cross area opposite to the weld line, at mid thickness over the weld zone utilizing 100 gf load¹³.



Figure 1. Fixture.

Table 1. Working parameters

process parameters	level 1	level 2	level 3
A Tool rotational speed(rpm)	800	1100	1400
B Tool feed rate(mm/min)	120	150	180
C Tool pin profile	Taper threaded	Cylindrical threaded (tpi-22)	Cylindrical threaded (tpi-14)

3. Analysis of Hardness

Hardness is the measure of resistance which material offers to change in shape. The information about the metallurgical changes caused by welding is provided by hardness measurement test. It was observed that with the increase of rotational speed there is increase in hardness, this is because of the reason that as a result of increased rotational speed more heat was generated due to which at recrystallization fine grains were formed which resulted in increased hardness. There was difference in hardness profiles formed at different tool rotational speeds, tool feed rate and tool pin profiles. From readings shown in the Table 2, the base composite hardness was found more as compared to normal hardness at zone of nugget. The micro hardness values changes in the welded territory and the parent material as microstructure of base alloy and joined zone are different. It was watched that with the expansion of rotational rate the hardness likewise expands, this is a result of the reason that as an after effect of expanded rotational speed more warmth was produced because of which at recrystallization fine grains were framed which brought about expanded hardness.

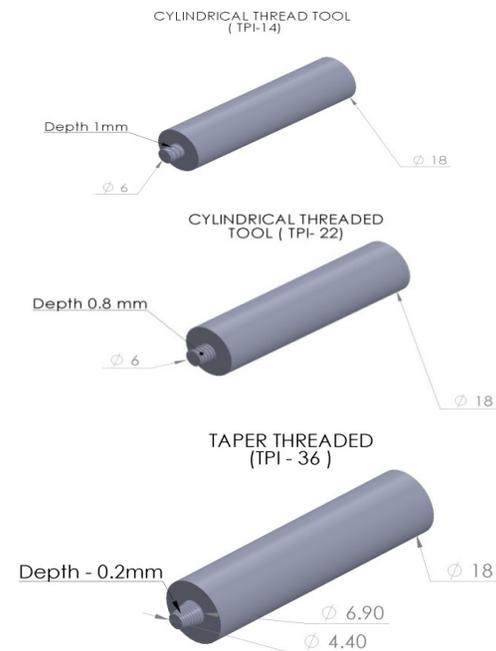


Figure 2. Tools used in the experiment.

Table 2. Microhardness (HV) at different distances from weld centre

Sr. no.	Microhardness (HV)								
	Distance from weld centre(mm)				Weld Centre	Distance from weld centre(mm)			
	AA6082-T6					AA6061-T6			
	8	6	4	2	2	4	6	8	
1	76.3	77.2	64.7	66.4	71.8	75.6	76.8	67.7	64.5
2	73.5	68.2	54.6	69.8	65.9	68.2	59.6	53.9	73.4
3	71.9	74.5	53.4	57.8	66.7	57.5	65.3	77	84.3
4	80.5	76.1	66.1	74.5	76.7	81.6	81	62.5	73.2
5	92.1	81.3	64.9	58.4	78.3	68.1	54.7	64	65.5
6	69.4	67.9	64.4	75	72.5	67.8	68.9	69.3	79.2
7	80.5	67.8	71.1	75.7	78	80.4	68.4	72.1	82.1
8	58.8	72.8	71.3	65.5	70.4	70.2	64.2	63.1	72.6
9	77.6	69.7	69	70.5	68.1	66.7	75.7	58.1	72.2

4. Conclusion

It was concluded from different observations on castings components during experimentation that hardness average value at zone of nugget was lower than the base alloy.

5. References

- Squillace A, Cavaliere P, Panella F. Effect of welding parameters on mechanical and micro structural properties of AA6056 joints produced by Friction Stir Welding. *Journal Materials Processing Technology*. 2006 Dec; 180(1-3):263–70.
- De Giorgi M, Scialpi A, De Filippis LAC, Nobile R, Panella FW. Mechanical analysis of ultra-thin Friction Stir Welding joined sheets with dissimilar and similar materials. *Materials and Design*. 2008 Jan; 29(5):928–36.
- Moreira PMGP, Santos TG, Tavares S, Richter-Trummer V, Vilaca P, de Castro PMST. Mechanical and metallurgical characterization of Friction Stir Welding joints of AA6061-T6 with w-T. *Materials and Design*. 2009 Jan; 30(1):180–7.
- Uematsu Y, Shibata TK, Tozaki HY, Ohmune T. Fatigue behaviour of Friction Stir Welds without neither welding flash nor flaw in several aluminium alloys. *International Journal of Fatigue*. 2009 Oct; 31(10):1443–53.
- Jacquín D, Meester B, Simar AD, Deloison D, Montheillet F, Desrayaud C. A simple Eulerian thermomechanical modelling of Friction Stir Welding. *Journal of Materials Processing Technology*. 2011; 211(1):57–65.
- Sreenivasan KS. Study of process parameters in Friction Stir Welding of dissimilar aluminium alloys. *Proceedings of the 2011 International Conference on Industrial Engineering and Operations Management*; Kuala Lumpur, Malaysia. 2011 Jan.
- Karthikeyan L, Senthil Kumar VS. Study of process parameters on mechanical properties of AA6063-T6 Aluminum alloy. *Materials and Design*. 2011 May; 32(5):3085–91.
- Azdas T, Bagheri A, Doniavi A. An experimental study on mechanical properties of Friction Stir Welded ABS sheets. *Materials and Design*. 2013 Jan; 43:402–9.
- Singh R, Kumar R. Effect of Friction Stir Welding on mechanical properties of dissimilar Aluminum Alloys. *International Journal of Computer Applications Proceedings on National Conference on Innovative Paradigms in Engineering and Technology (NCIPET 2012)*. 2012 Mar; 2(6):12–6.
- Prakash P, Jha S, Lal S. A study of process parameters of Friction Stir Welded AA6061 aluminum alloy. *International Journal in Innovative Research in Science Engineering and Technology*. 2013 Jun; 2(6):1–6.
- Duffie NA, Cole EG, Fehrenbacher A, Zinn MR, Pfeifferkorn FE, Ferrier NJ. Weld temperature effects during Friction Stir Welding of dissimilar aluminium alloys 6061-t6 and 7075-t6. *International Journal of Advanced Manufacturing Technology*. 2014 Mar; 71(1):643–52.
- Muthuvaideyanathan R. Effect of process parameters on Friction Stir Welding of 6063 aluminium alloy. *International Journal of Design and Manufacturing Technology*. 2015 Jan-Apr; 6(1):1–9.
- Azizieh M. Mechanical properties and micro structural evaluation of AA1100 to AZ31 dissimilar Friction Stir Welds. *Materials Chemistry and Physics*. 2016 Feb; 170:251–60.